



International Journal of Emerging Technology and Advanced Engineering

Website: www.ijetae.com (ISSN 2250-2459, ISO 9001:2008 Certified Journal, Volume 4, Special Issue 4, June 2014)

International Conference on Advances in Civil Engineering and Chemistry of Innovative Materials (ACECIM'14)

Study on Shallow Funicular Concrete Shells over Rectangular Ground Plan Ratio 1:0.9

P. Sachithanantham¹, Dr. S. Sankaran², Dr. S. Elavenil³

¹Research Scholar, Department of Civil Engineering, Bharath University, Chennai, Tamilnadu, India.

²Professor and Dean, Department of Civil Engineering, Arunai College of Engineering, Tiruvannamalai, Tamilnadu, India.

³Professor, Department of Civil Engineering, VIT University, Chennai, Tamilnadu, India.

¹sachu_civil@yahoo.co.in, ²sankaran_bit@yahoo.co.in, ³s_elavenil@yahoo.com

Abstract— Shells, stressed skin structures because of their geometry and small flexural rigidity of the skin, tend to carry loads primarily by direct stresses acting in their plane. Concrete shallow funicular shells of rectangular ground plan, double curvature with different rises are loaded to failure with a concentrated central force. Specimens of size 100 cm x 90 cm in plan with edge beam of size 4cm x 4cm are prepared with concrete of grade M30 for which the mix design is carried by Indian Standard method. The specimens are prepared with various rises and moist cured. They are subjected to ultimate loads and the corresponding strains and deflections are measured. Failure patterns for shells with different rises are observed. From the experimental investigations a relation between span to rise ratio and ultimate load is arrived. It is concluded that the ultimate loads are function of the rise of the shell.

Keywords—Shells, Concrete shell, Funicular shell, Ultimate load, span to rise ratio

I. INTRODUCTION

Shells belong to the class of stressed skin structures which, because of their geometry and small flexural rigidity of the skin, tend to carry loads primarily by direct stresses acting in their plane (1). In the design of new forms of concrete shell structures the conventional practice is to select the geometry of shell first and then making the stress analysis. In this process no deliberate effort is taken to ensure the desirable state of stress in the material. Perhaps it is more logical to reverse this process. Ideally a concrete shell in its membrane state carries the external loads by pure compression, unaccompanied by shear stresses so that no tensile stresses develop and hence the reinforcement becomes necessary excepting for secondary effects like bending, shrinkage.

In most of the shell roof the predominant load is the dead weight. Hence it is advantageous to select the shape of shell in such a way that, under this condition of loading, the shell is subjected to pure compression without bending. This can be achieved by shaping the shell in the form of a catenary which the funicular shape is corresponding to the dead weight (2). Shell of rectangular and square ground plans are very frequent occurrence in practice. An attempt is made to study the influence of rise on the ultimate load of the Shallow Funicular Concrete Shells of rectangular Ground Plan ratio of 1:0.9

John W Weber et al., observed that the mathematical investigations of shallow funicular shells with large concentrated loads should be based on large deflection theory and the deflection characteristics of a shell vary closely with its rise parameter (3). Patricia M Belles et al., conclude that the analysis of the stresses and deformations of concrete shell with the anti funicular shape found with the homeostatic model technique (HMT) allows the verification of quasi membrane behaviour (4). Vafai and Farshad studied that the experimental failure loads are found to be directly related to the amount of reinforcement and the age of concrete shells (5). Sachithanantham et al, concluded that the deflection of shallow funicular concrete shells decrease with increase in rise within elastic range and also concluded that the ultimate load carrying capacity increases with increase in rise (6).



International Journal of Emerging Technology and Advanced Engineering

Website: www.ijetae.com (ISSN 2250-2459, ISO 9001:2008 Certified Journal, Volume 4, Special Issue 4, June 2014)

International Conference on Advances in Civil Engineering and Chemistry of Innovative Materials (ACECIM'14)

II. METHODOLOGY

A. Materials

Concrete funicular shell specimens of various rises are prepared with cement, fine aggregate and coarse aggregate for which the design mix proportion is arrived as shown in table II. To investigate the influence of different rises on the ultimate strength of shallow funicular shells, specimens are prepared and designated as follows.

- i) SFS I – Shallow Funicular Shell with rise (r1) – 9.2 cm
- ii) SFS II – Shallow Funicular Shell with rise (r2) – 12.2 cm
- iii) SFS III – Shallow Funicular Shell with rise (r3) – 13.7 cm

Preliminary tests are carried as per IS standards on the material used for concrete like specific gravity, fineness, consistency, and initial setting time for cement. For fine and coarse aggregates tests such as sieve analysis, specific gravity, impact value, crushing value and abrasion value (Los Angeles and Deval's) are conducted as per standards(7)(8) and the results are tabulated.

B. Mix Design

Concrete used for the investigation is designed in accordance with IS 10262 (9).

Test Data for Materials

Cement used	-PPC – 53 grade
Specific gravity of Cement	- 3.15
Specific gravity of coarse aggregate-	2.76
Specific gravity of Fine aggregate -	2.65
Water absorption	
Coarse aggregate	- 0.3%
Fine aggregate	- 2.9%
Free surface moisture	
Coarse aggregate	- Nil
Fine aggregate	- 2.6%
Sieve analysis	
Coarse aggregate - Confirms grading of IS 383 - 1973	
Fine aggregate - Confirms zone - II	

The design stipulations for M30 grade concrete is given in table I.

TABLE I
DESIGN STIPULATIONS FOR M30 GRADE CONCRETE

Design Stipulations	M30
Characteristic Compressive Strength	30 N/mm ²
Maximum size of aggregates	10 mm (angular)
Degree of Workability	0.85 (Compacting Factor)
Type of Exposure	Mild
Degree of Quality Control	Very Good

TABLE II
DESIGN MIX PROPORTION

Grade	Cement	Fine Aggregate	Coarse Aggregate	w/c ratio
M30	1	1.327	2.255	0.47

C. Preliminary Investigations

The following tests are conducted on cement, fine aggregate and coarse aggregate and the results are tabulated in table III.

TABLE III
TEST ON CEMENT, FINE AGGREGATE AND COARSE AGGREGATE

Materials	Properties	Values
Cement	Specific Gravity	3.15
	Fineness, %	95.32
	Consistency, %	32
	Initial Setting time, min	38
Fine Aggregate	Specific Gravity	2.65
	Gradation	Zone II
Coarse Aggregate	Specific Gravity	2.76
	Impact Value, %	26.30
	Crushing Value, %	15
	Los Angeles Abrasion Value, %	8



International Journal of Emerging Technology and Advanced Engineering

Website: www.ijetae.com (ISSN 2250-2459, ISO 9001:2008 Certified Journal, Volume 4, Special Issue 4, June 2014)

International Conference on Advances in Civil Engineering and Chemistry of Innovative Materials (ACECIM'14)

D. Casting of Shallow Funicular Pre moulds

Concrete funicular pre moulds of size 100cm x 90cm in ground plan are prepared using cement concrete. A steel frame along with polyurethane membrane is used for casting the pre moulds. The edges of poly urethane membrane is stretched between the boundaries of the rectangular steel frame of ground plan ratio 1: 0.9 and clamped. Concrete with very high workability is poured over the membrane due to which the membrane sags downwards and forms a funicular shape. The downward sag is controlled by adjusting the membrane with the clamps provided at the edges as shown in fig.1. After the concrete has set the pre moulds are removed from the frame and the membrane which is used as form work for casting the moulds.



Fig.1 Rectangular steel frame with poly urethane membrane for casting the pre mould

E. Casting of Shallow Funicular Moulds

Concrete funicular moulds of size 100cm x 90cm in plan with provision of edge beam of 4cm x 4cm are prepared using cement concrete with adequate reinforcement. Fabrication of mould is in such a way that the moulding of four edge beams are provided as an integral component of each shell mould. Reinforcement of 4mm diameter GI bars are provided in both directions with spacing of 160mm c/c. By repeating this process shell moulds of various rises are prepared as shown in Fig 2.



Fig.2 Moulds of Shallow Funicular Shells

F. Casting of Shallow Funicular Shells

Concrete funicular shells of size 100cm x 90cm in plan with edge beam of 4cm x 4cm are prepared using cement concrete of grade M30 with 4mm diameter GI wires at a spacing of 75mm c/c as reinforcement. Rectangular Shell specimens are prepared with shell moulds with various rises of 9.2 cm (r1), 12.2 cm (r2) and 13.7 cm (r3) as shown in Fig 3 and 4. Care is taken to maintain the uniform thickness of funicular shell as 25mm with the help of measuring gauge. The shell specimens are moist cured.



Fig.3 Casting of shell specimen



Fig.4 Shell specimens with various rises



III. EXPERIMENTAL SETUP AND TESTING

The self-straining load frame and the Hydraulic loading jack along with Load cell are arranged in such a way to apply the concentrated force over the centre of the shell specimen as shown in Fig. 5(a) and 5(b). Care is taken to avoid eccentricity during loading. Linear Variable Differential Transformer (LVDT) and strain gauges are mounted where the deflection and strain are required in the specimen. To facilitate the locations of LVDT and strain gauge the specimens are specially painted and the surface of the shell is discretized with 360 elements of size of 50mm x 50mm. Specimens and the grids are marked as shown in Fig. 6. The rise of the shell specimens cast are measured using Total Station and it is observed that the rises are almost equal to the predetermined values. Shells of SFS I, SFS II and SFS III are placed on loading frame and subjected to central concentrated force and the corresponding deflections are measured within the elastic range using a 20 channel data acquisition system.



Fig. 5 (b) Experimental Setup

After the elastic range all the specimens are subjected to failure and hence the ultimate loads are recorded in the data acquisition system. Visible cracks first appeared at the centre of the shell's outer surface and then propagated towards the corners along the diagonals. As the load is increased apparent zones of tension near and approximately parallel to the supports are also cracked by which the shell eventually failed. The crack patterns of shell specimens are shown in fig. 7.



Fig. 5 (a) Experimental Setup

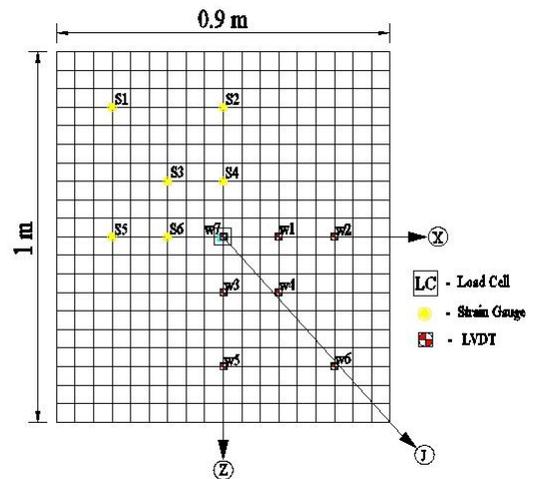


Fig. 6 Discretized Shell specimen

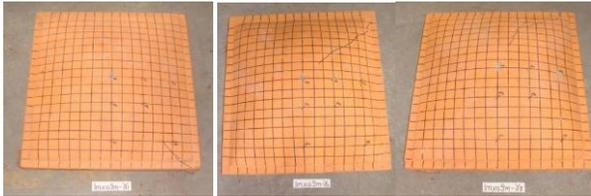


Fig. 7 Crack patterns of shell specimens

IV. RESULTS AND DISCUSSIONS

From the experimental investigations of SFS I, SFS II and SFS III a plot is made between the load and the corresponding deflection as shown in fig. 8, 9 and 10 for rise r1, r2 and r3 respectively.

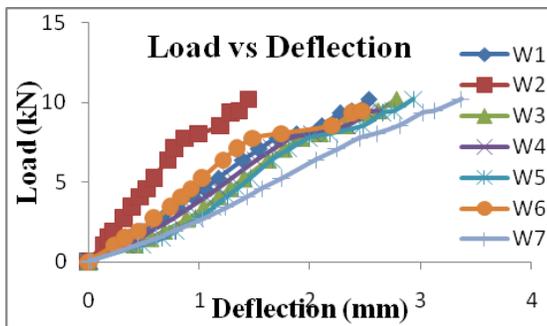


Fig.8 Load vs deflection, r1

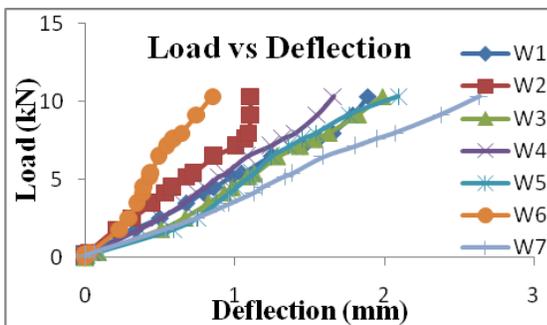


Fig.9 Load vs deflection, r2

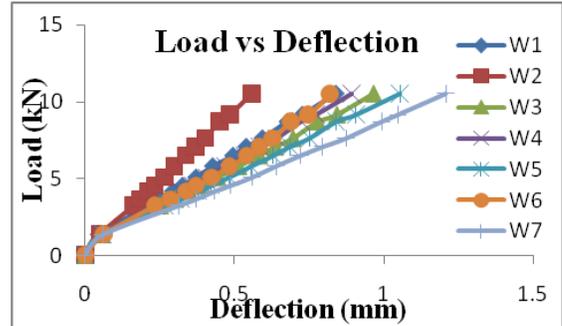


Fig.10 Load vs deflection, r3

From the figures 8, 9 and 10 it is observed that the deflection of shallow funicular concrete shell decreases with increase in rise. The ultimate loads for the specimens are tabulated in table IV.

**TABLE IV
 TEST RESULTS OF ULTIMATE LOAD (PU) FOR SHELLS**

Type	Rise, (h)	Span/Rise ratio, (λ)	Ultimate Load, Pu (kN)
SFS I	9.2	9.78	20.60
SFS II	12.2	7.37	21.59
SFS III	13.7	6.57	26.48

A plot is made between ultimate load and the rise of the shell as shown in Fig 11. It is observed that the ultimate load increases with increase in rise. A plot is made between ultimate load and span to rise ratio (λ) as shown in Fig 12.



International Journal of Emerging Technology and Advanced Engineering

Website: www.ijetae.com (ISSN 2250-2459, ISO 9001:2008 Certified Journal, Volume 4, Special Issue 4, June 2014)

International Conference on Advances in Civil Engineering and Chemistry of Innovative Materials (ACECIM'14)

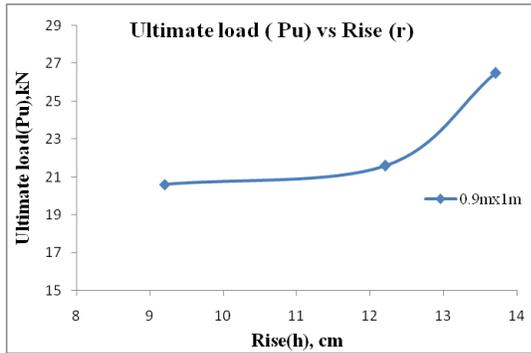


Fig. 11 Ultimate load vs Rise

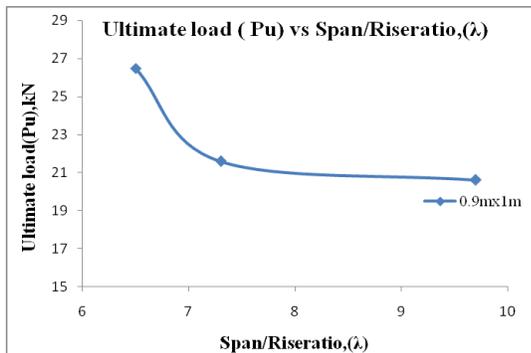


Fig.12 Ultimate load vs Span /rise ratio (λ)

From Fig 11, it is observed that the ultimate load (Pu) increases with the decrease in span to rise ratio (λ). From the fig. 12 the relationship between Pu and λ can be approximated by the equation (1) where λ value lies (5 < λ < 20).

$$Pu = 1.781\lambda^2 - 30.69\lambda + 150.7 \dots\dots\dots (1)$$

V. CONCLUSIONS

From the experimental investigations it is concluded that the deflection of shallow funicular concrete shell decreases with the increase in rise within the elastic range. The ultimate load carrying capacity increases with the increase in rise. It is also concluded that an increment of 4.58 % of ultimate load (Pu) is observed in SFS I when compared with SFS II., an increment of 18.46% and 22.20% of ultimate load (Pu) is observed in SFS III when compared with SFS II and SFS I respectively.

REFERENCES

- [1] IS: 2210 - 1988, "Criteria for Design of reinforced Concrete shell Structures and folded plates", Bureau of Indian Standards, 1989.
- [2] Ramasamy G. S, "Design and Construction of Concrete Shell Roofs", CBS publishers, 1986.
- [3] John W Weber et al, "Ultimate Loads for Shallow Funicular Concrete Shells", Northwest, Vol. 58, No. 3, 1984, pp 187 – 194.
- [4] Patricia M Belles et al, ' Virtual Simulation of Shape Generation of Homeostatic Shell Models', Association Argentina, *Mechanica Computational*, Vol 25, Nov, 2006, pp 549 – 560
- [5] Vafai. A and M. Farshad, (1979) "Theoretical and Experimental Study of Prefabricated Funicular Shell Units", *Building and Environment*, Vol. 14, No. 3, pp. 209-216.
- [6] Sachithanatham.P, Elavenil.S and Sankaran.S, (2011) " Study on Shallow Funicular Concrete Shells over Square Ground Plan Subjected to Ultimate loads", *International Journal of Earth Sciences and Engineering*, Vol.4, No.06 Spl., Oct 2011, pp 632-637.
- [7] IS: 383-1970, "Coarse and fine aggregate from natural sources for concrete", Indian Standards Institution, 1970.
- [8] IS: 2386 (Part I – IV) - 1963, "Methods of Test for Aggregates for Concrete", Bureau of Indian Standard, 1963.
- [9] IS: 10262-1982, "Recommended guidelines for concrete mix design", Indian Standards Institution, 1982.
- [10] Farshad.M, and G. Ahmadi,(1979) "Influence of Loading Behavior on the Stability of Cylindrical Shells", *J. of Sound and Vibration*, Vol. 62, No. 4, pp. 533-540.
- [11] Kai-uwe bletzinger, Linhard J, Wüchner R, Bletzinger KU,(2009) "Isogeometric shell analysis with Kirchhoff-Love elements". *Comp. Meth. Appl. Mech. Engng*.198: pp 3902-3914.
- [12] IS: 2210 - 1988, "Criteria for Design of reinforced Concrete shell Structures and folded plates", Bureau of Indian Standards, 1989.
- [13] IS: 2204 - 1962, "code of practice for construction of reinforced concrete shell roof", Bureau of Indian Standards, 1962.